



Mechanical Properties of Cork: Effect of Hydration

Aurélie Lagorce-Tachon, Thomas Karbowiak, Dominique Champion, Régis D. Gougeon, Jean-Pierre Bellat

► To cite this version:

Aurélie Lagorce-Tachon, Thomas Karbowiak, Dominique Champion, Régis D. Gougeon, Jean-Pierre Bellat. Mechanical Properties of Cork: Effect of Hydration. World Automation Congress (WAC 2014), Mar 2014, Beaune, France. 2014. hal-04255494

HAL Id: hal-04255494

<https://u-bourgogne.hal.science/hal-04255494>

Submitted on 24 Oct 2023

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Mechanical properties of cork: effect of hydration

Aurélie TACHON^{a,b,c}, **Thomas KARBOWIAK**^a, **Dominique CHAMPION**^a,
Régis GOUGEON^{a,b} and **Jean-Pierre BELLAT**^c

^a UMR PAM Équipe PAPC Agrosup Dijon, Université de Bourgogne, 1 esplanade Erasme, F-21078 Dijon, France

^b Institut Universitaire de la Vigne et du Vin, Université de Bourgogne, 1 rue Claude Ladrey, F-21078 Dijon, France

^c Laboratoire Interdisciplinaire Carnot de Bourgogne, UMR 6303 CNRS, Université de Bourgogne, 9 avenue Alain Savary, B.P. 47870 F-21078 Dijon, France

Context

The use of cork as sealing for wine bottles is due to its low permeability to liquids and gases, imputrescibility and good mechanical properties, in particular its remarkable elasticity [1-2].


Objectives

- To determine mechanical properties of cork along the radial and tangential directions (which corresponds to the compression in a bottleneck)
- To study the effect of hydration on mechanical properties of cork


Materials & Methods

Cork

- Species: *Quercus suber* L.
- Origin: Portugal
- High quality (class 0)
- neither washed nor surface treated

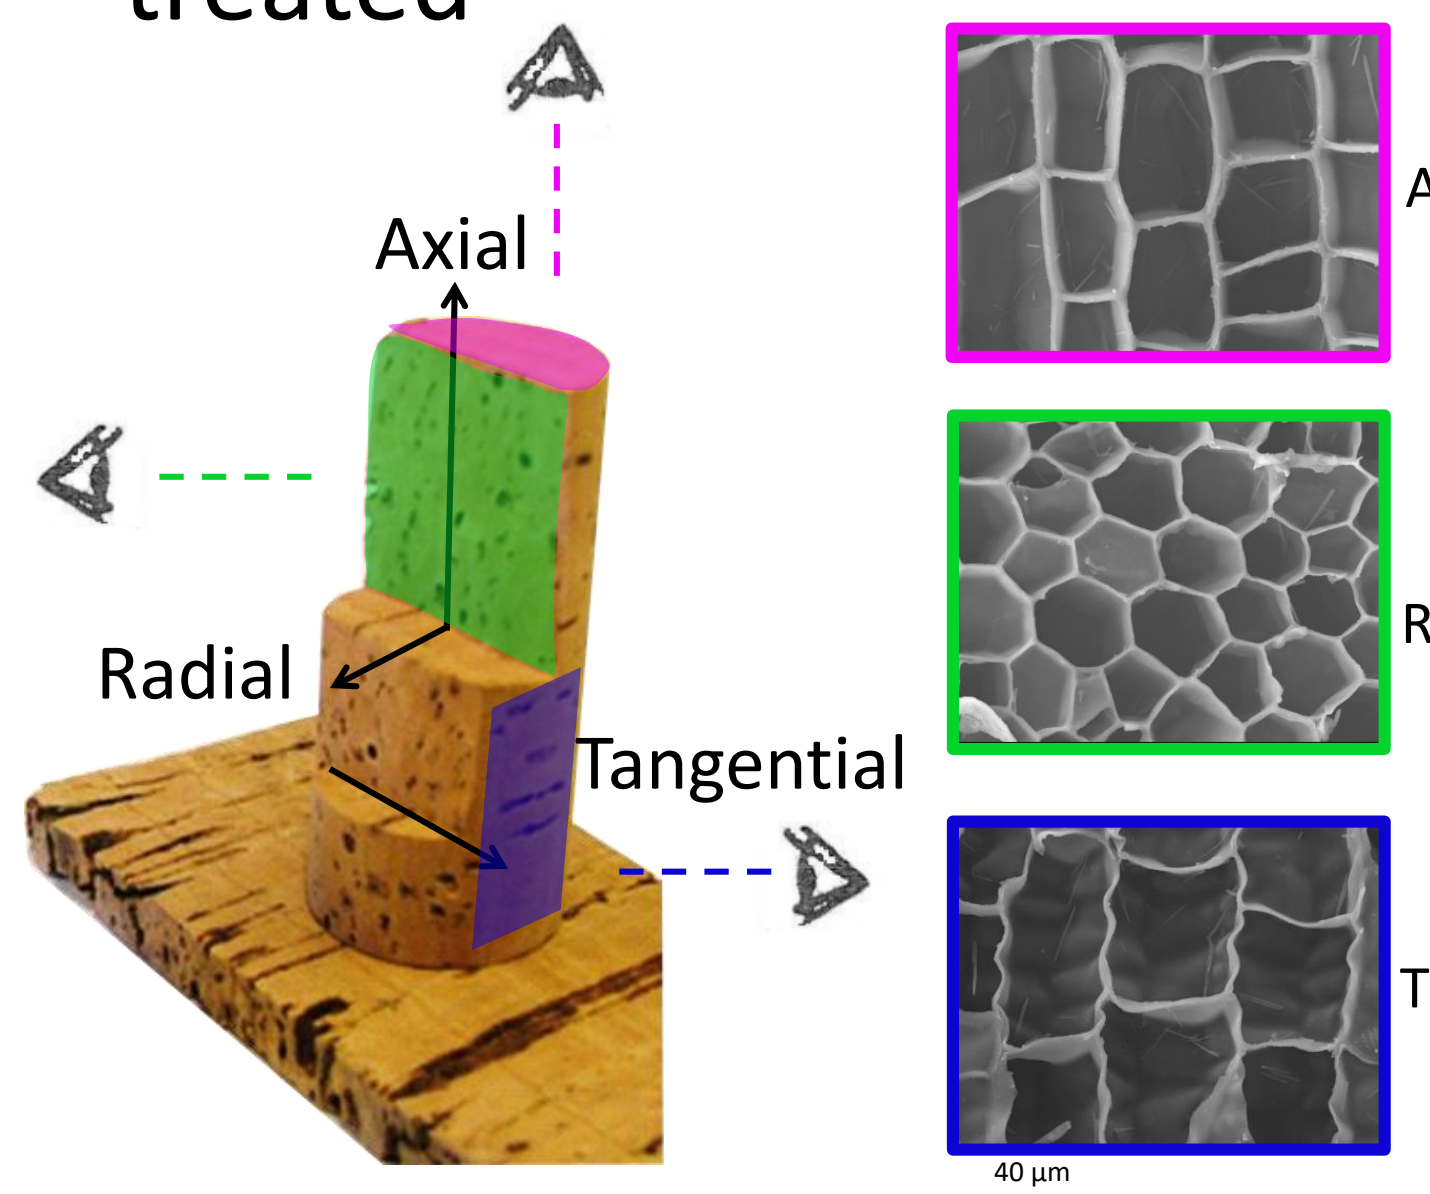

Sample preparation

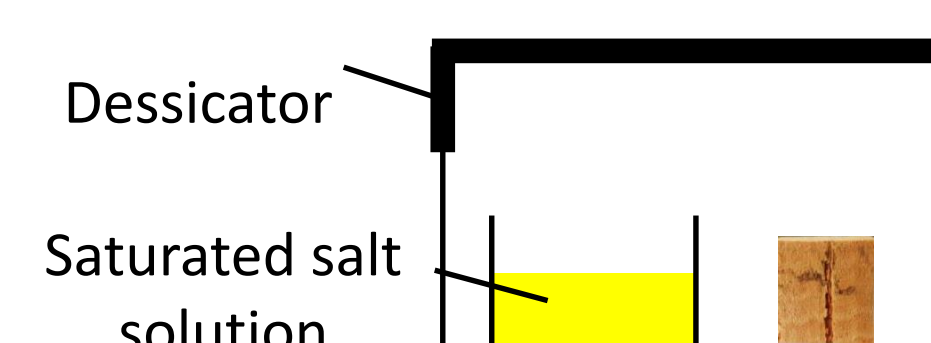


RH from 0 to 100 %
T = 25°C
Equilibration time ≈ 4 months

Compression test

TA-HD⁺


Deformation: 80 %

Test speed: 1 mm/sec

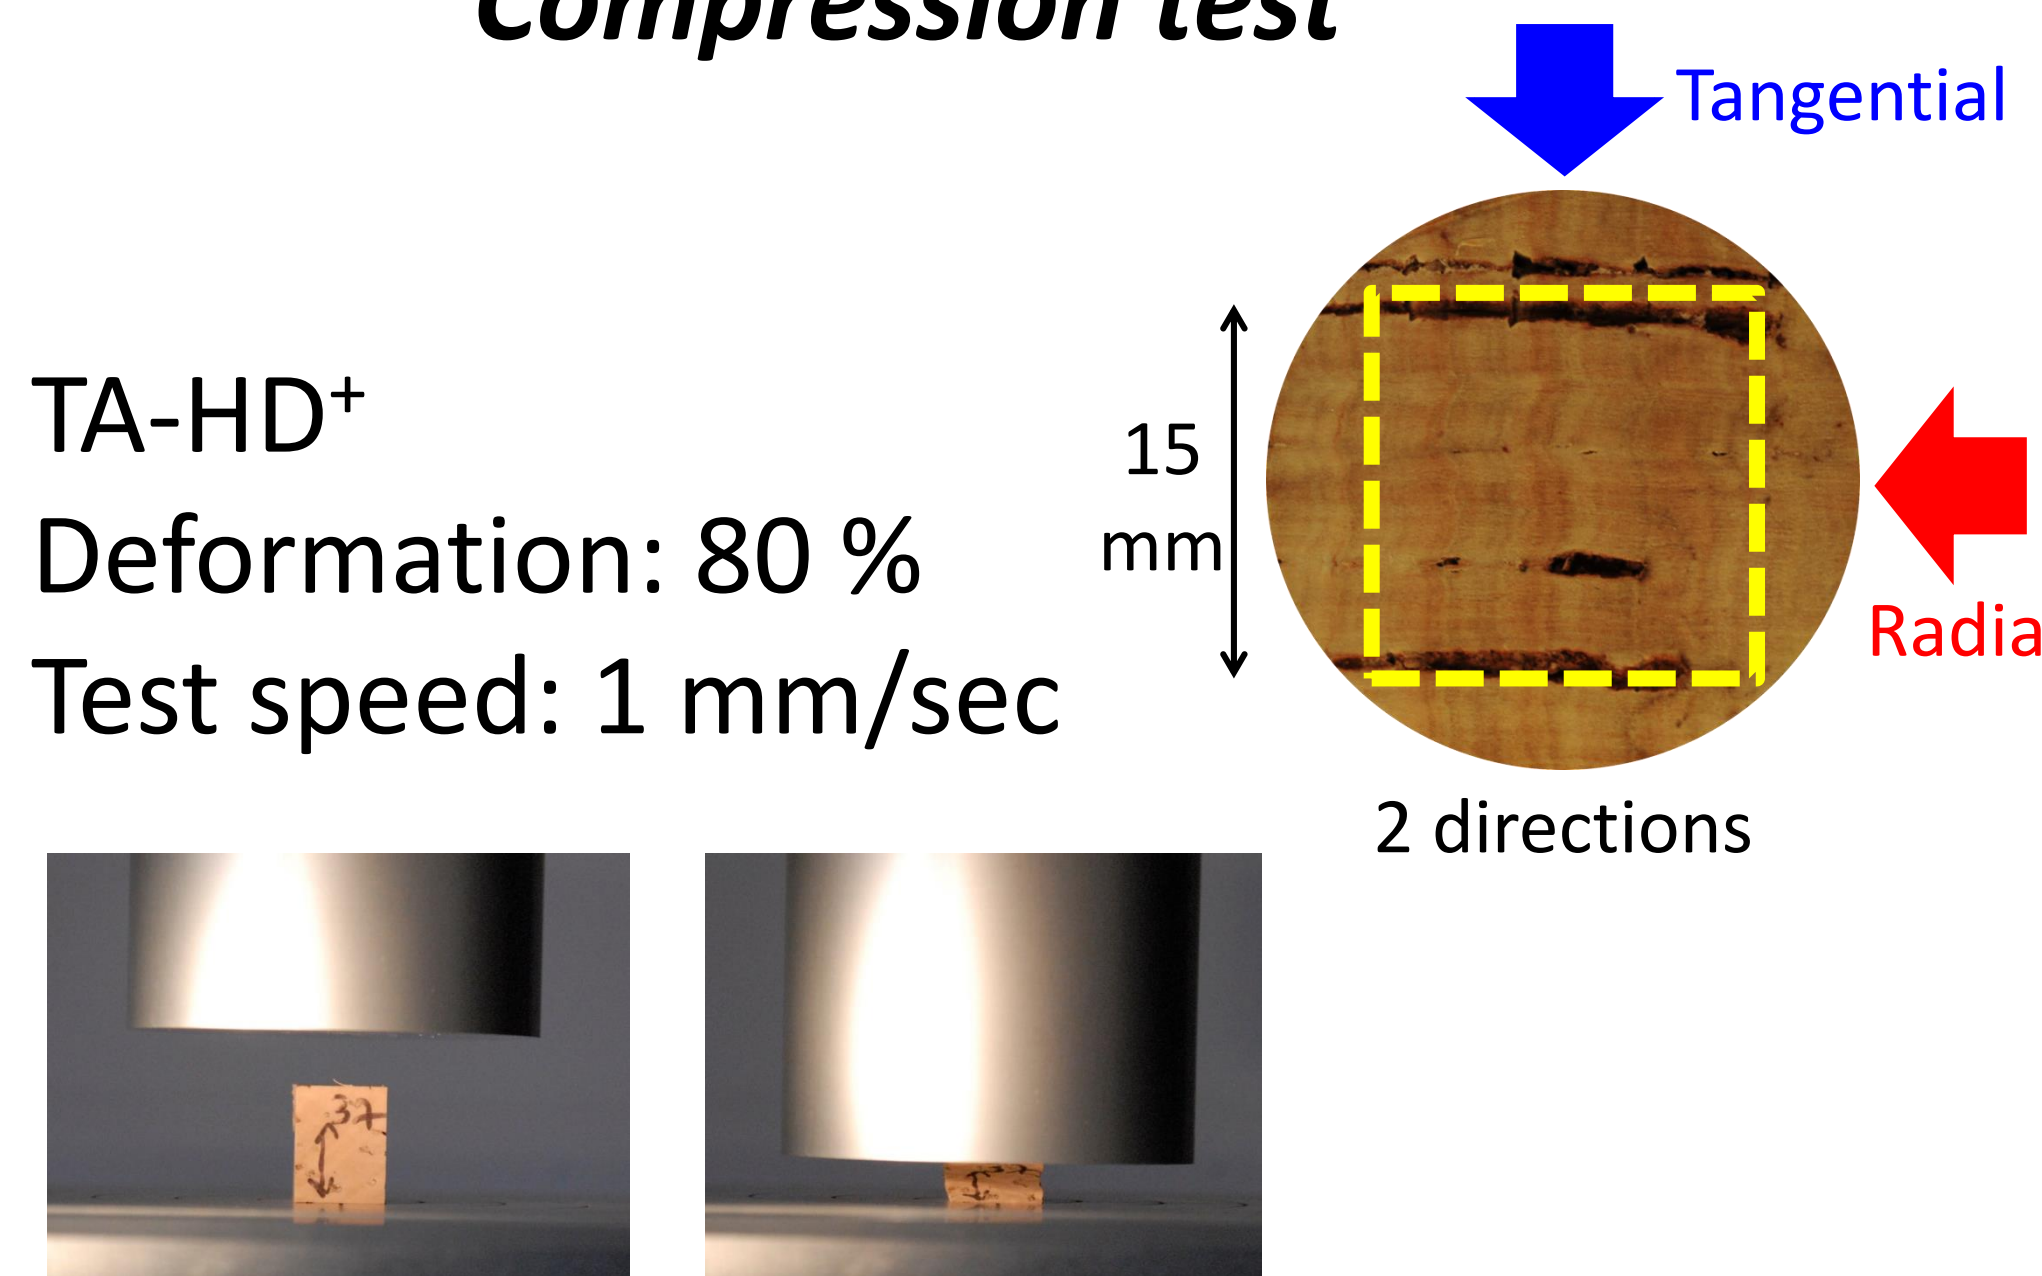

Results

Cork under compression

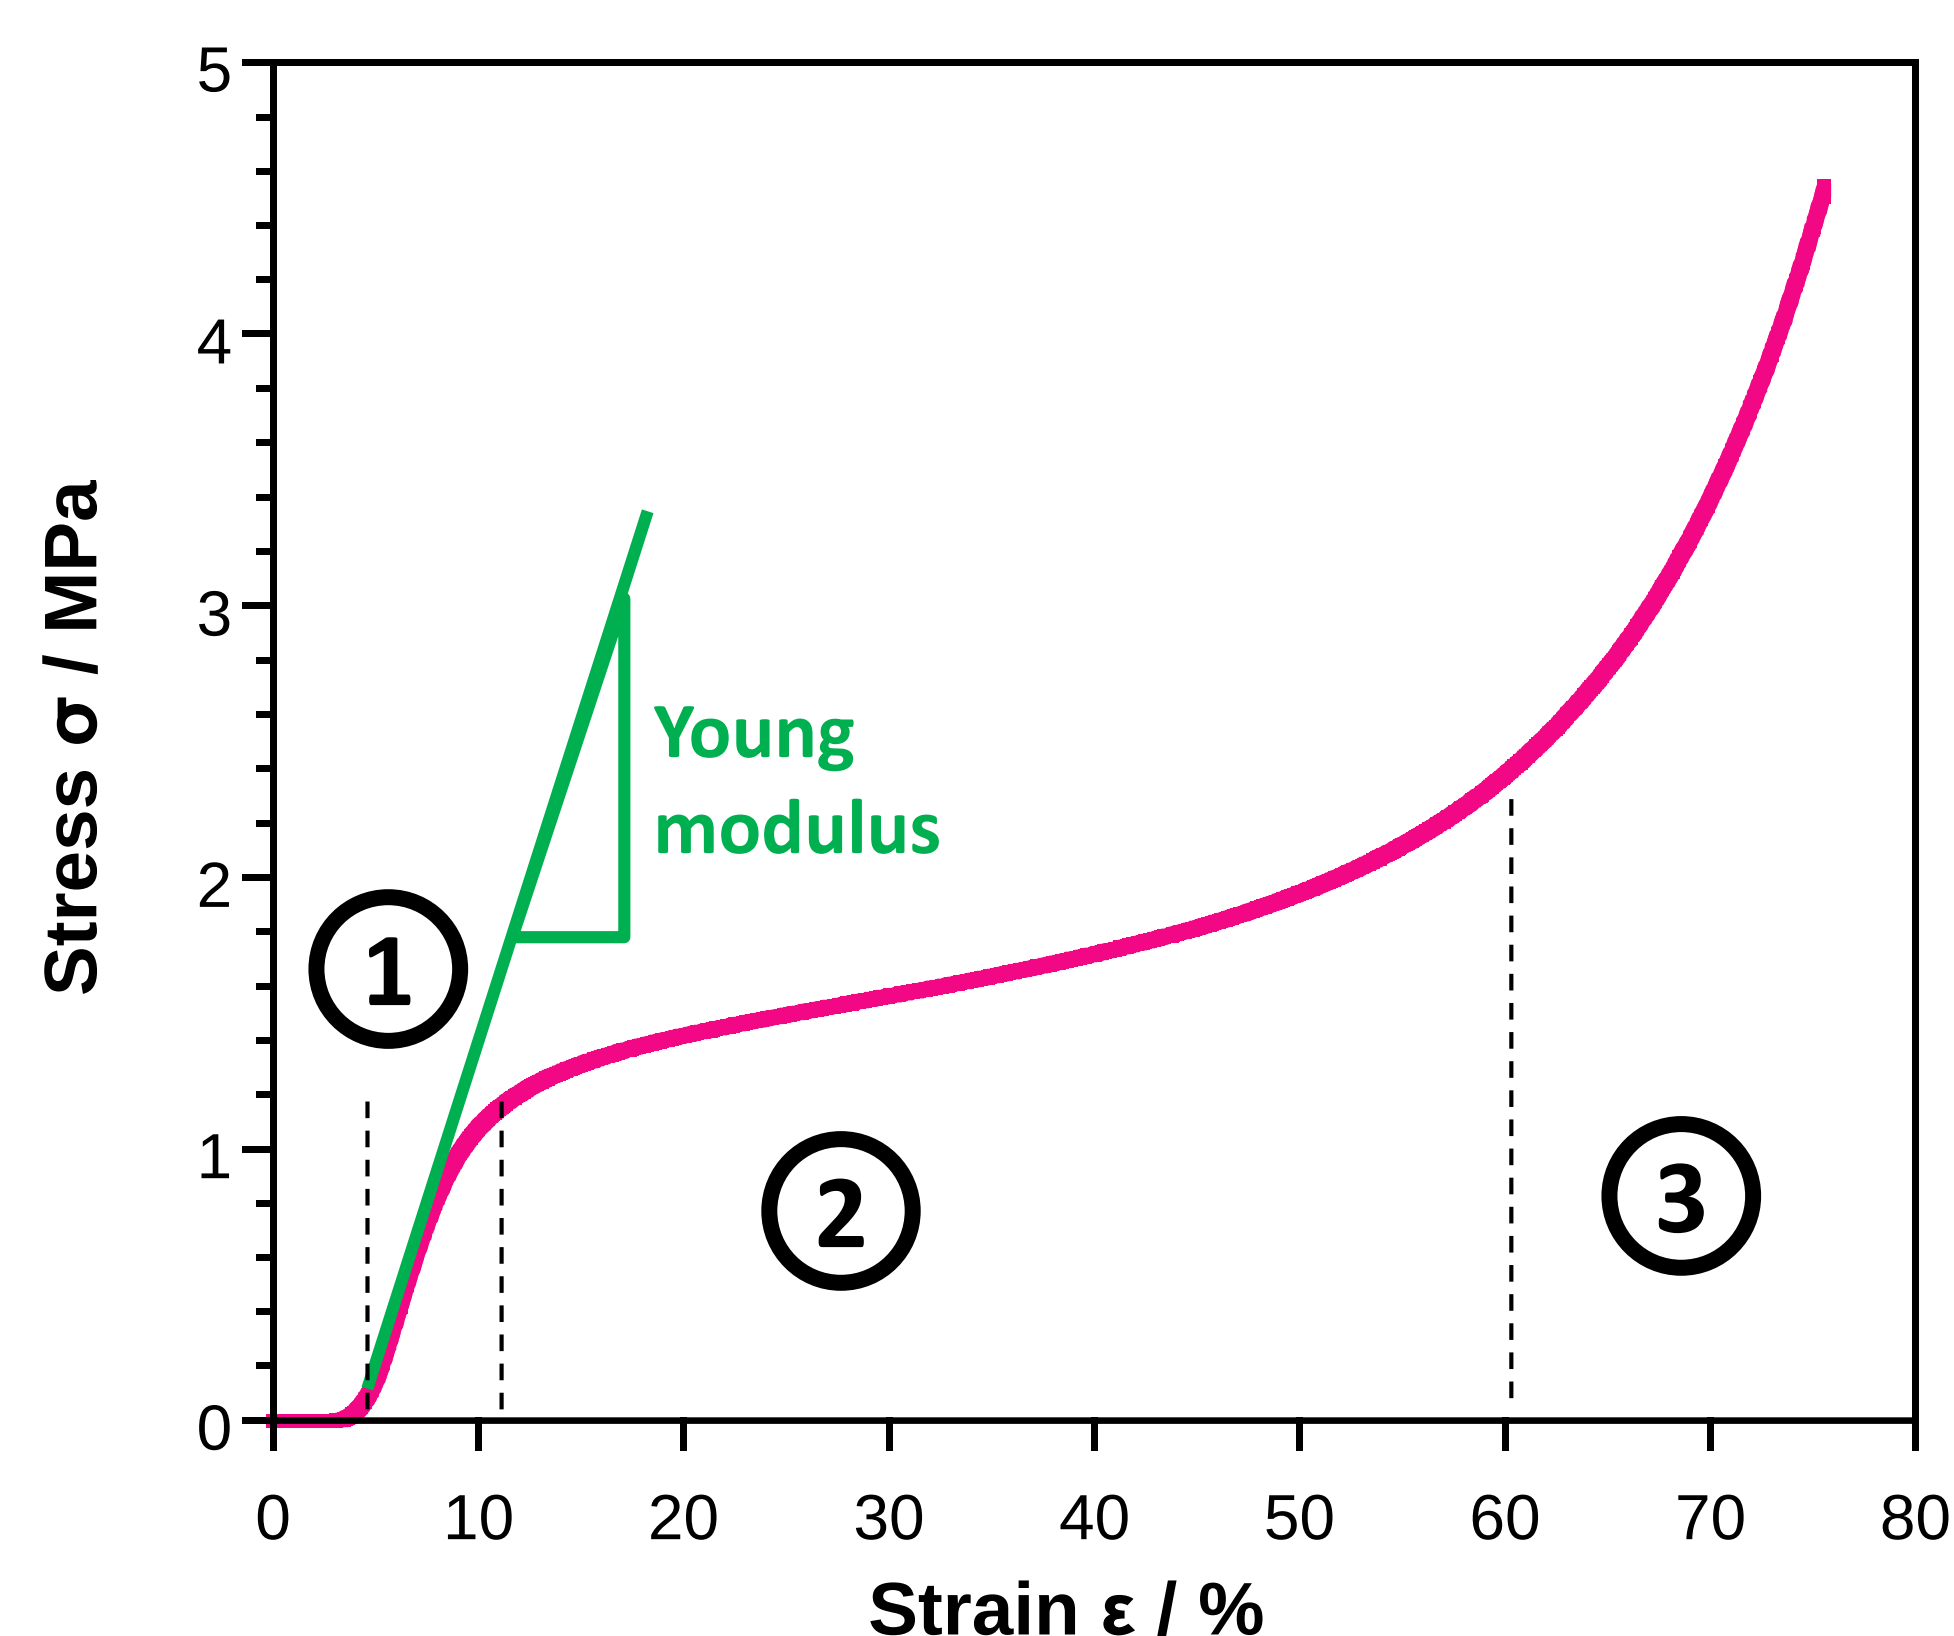


→ strain/stress curve:
3 regions

- 1 Elastic region
- 2 progressive buckling of cell walls
- 3 buckling of cell walls


Young modulus calculation

$$E = \frac{\sigma}{\varepsilon}$$

Water effect on Young modulus

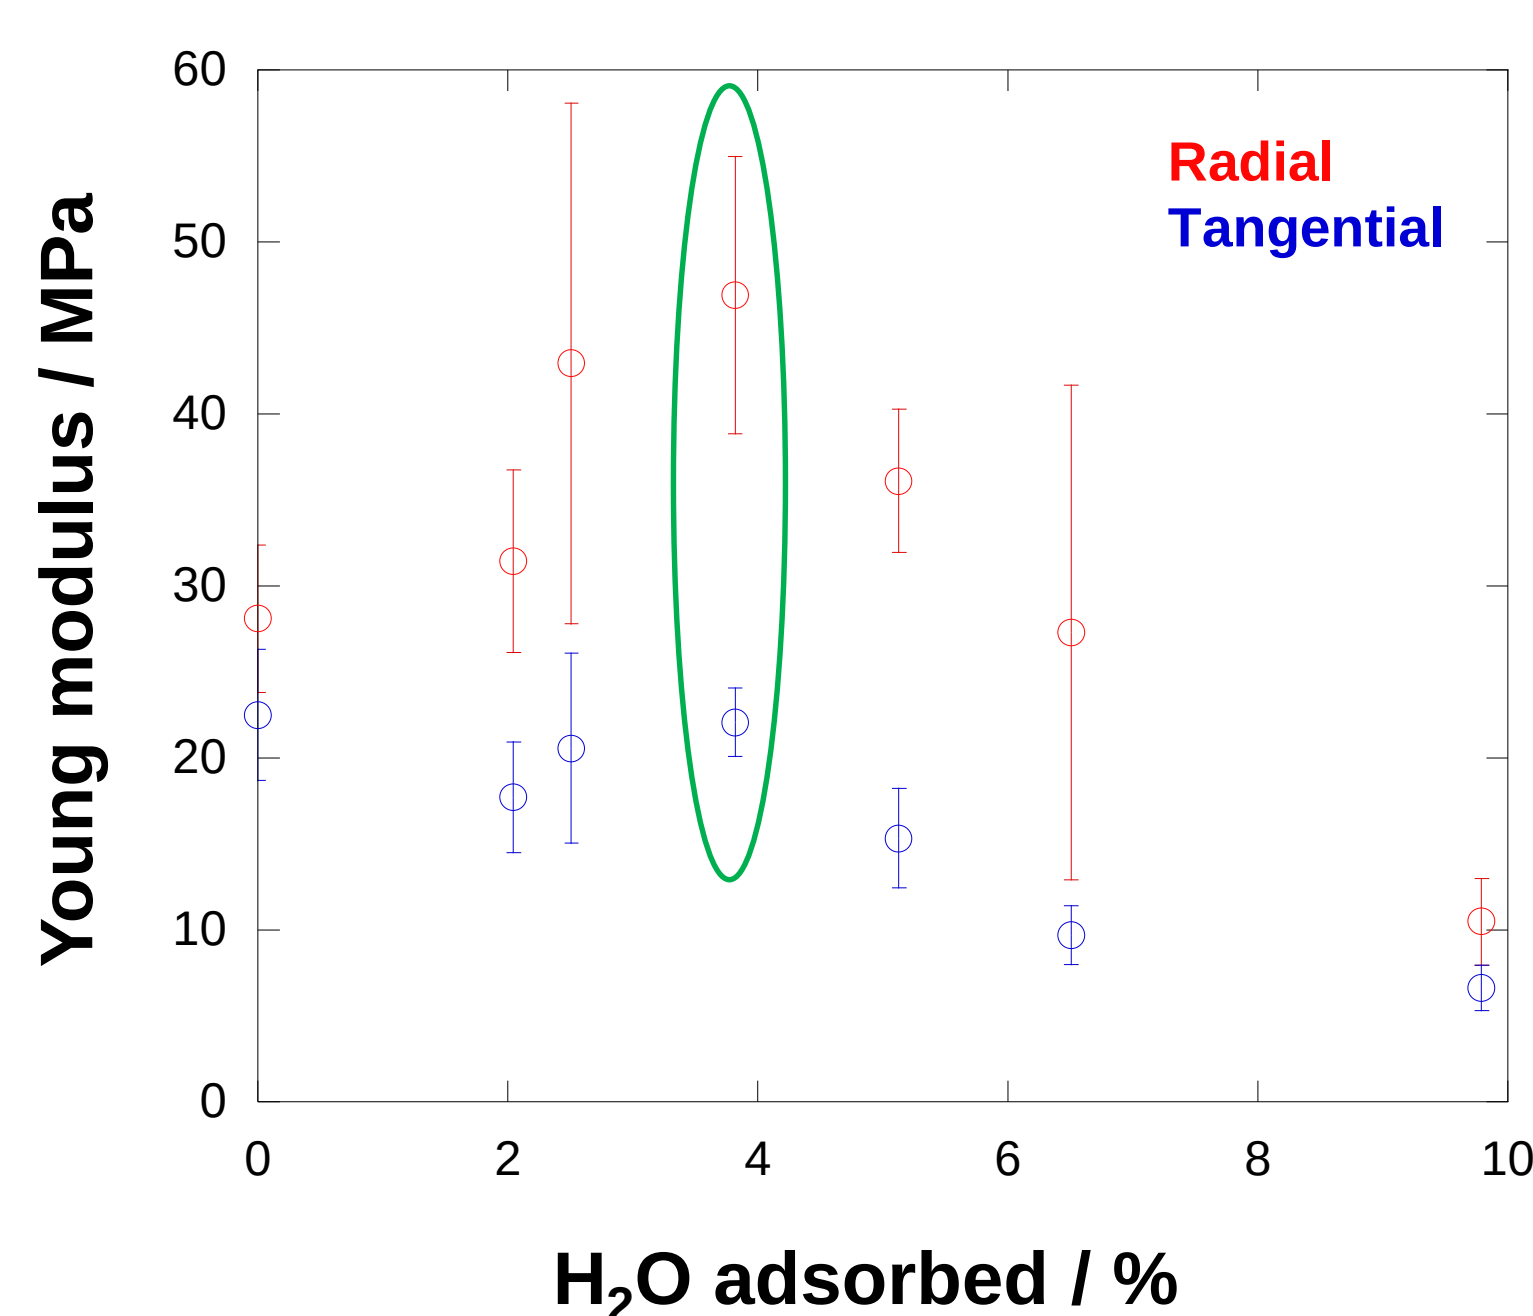


→ Rigidity: - radial > tangential
- maximum for HR ≈ 50%

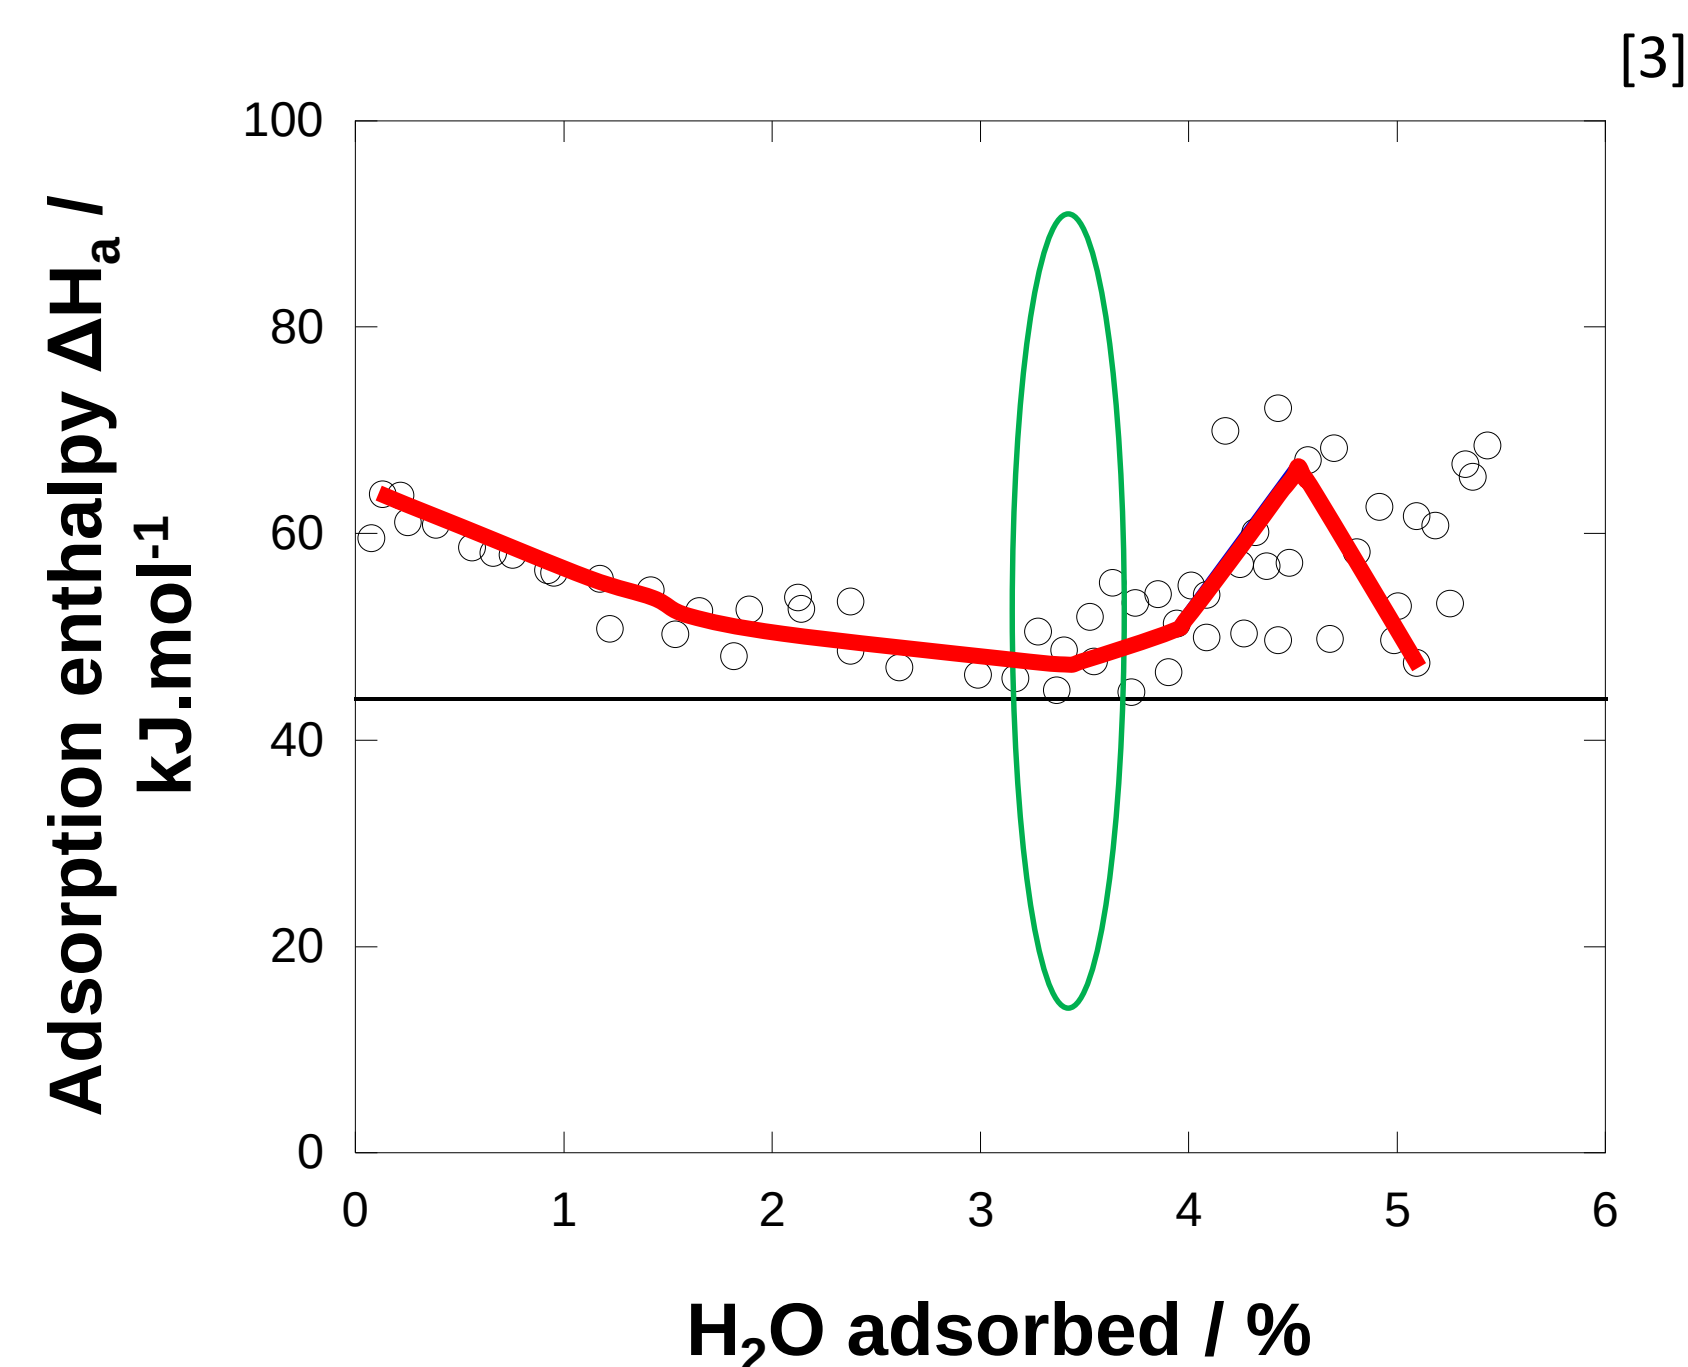

→ Important role of water in cork structure


Dynamic mechanical analysis

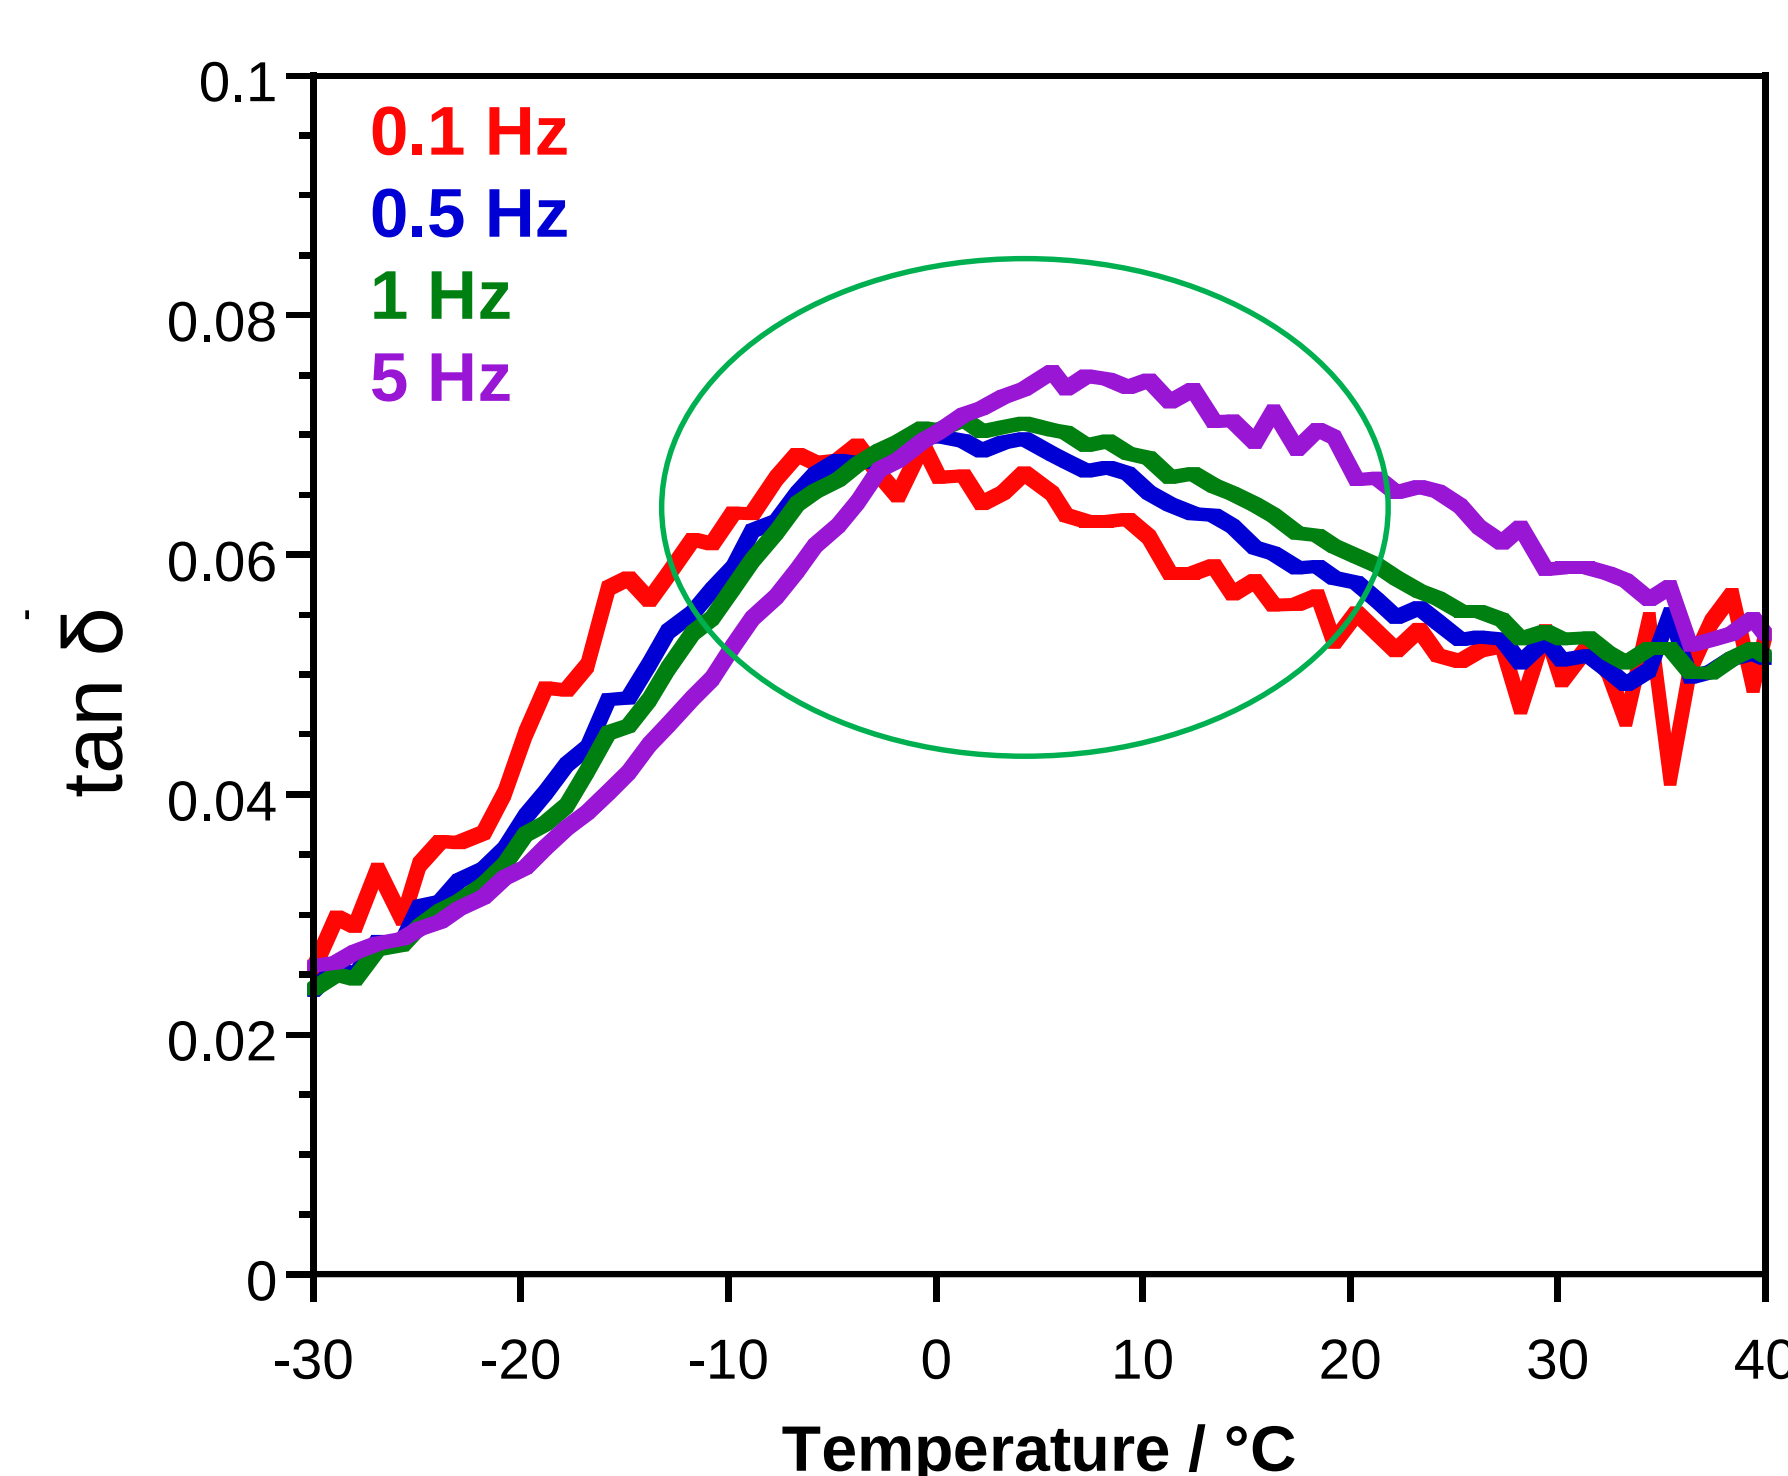

$$\tan \delta = \frac{G''}{G'}$$

→ Shift of tan δ for different frequencies: glass transition?

Differential scanning calorimetry

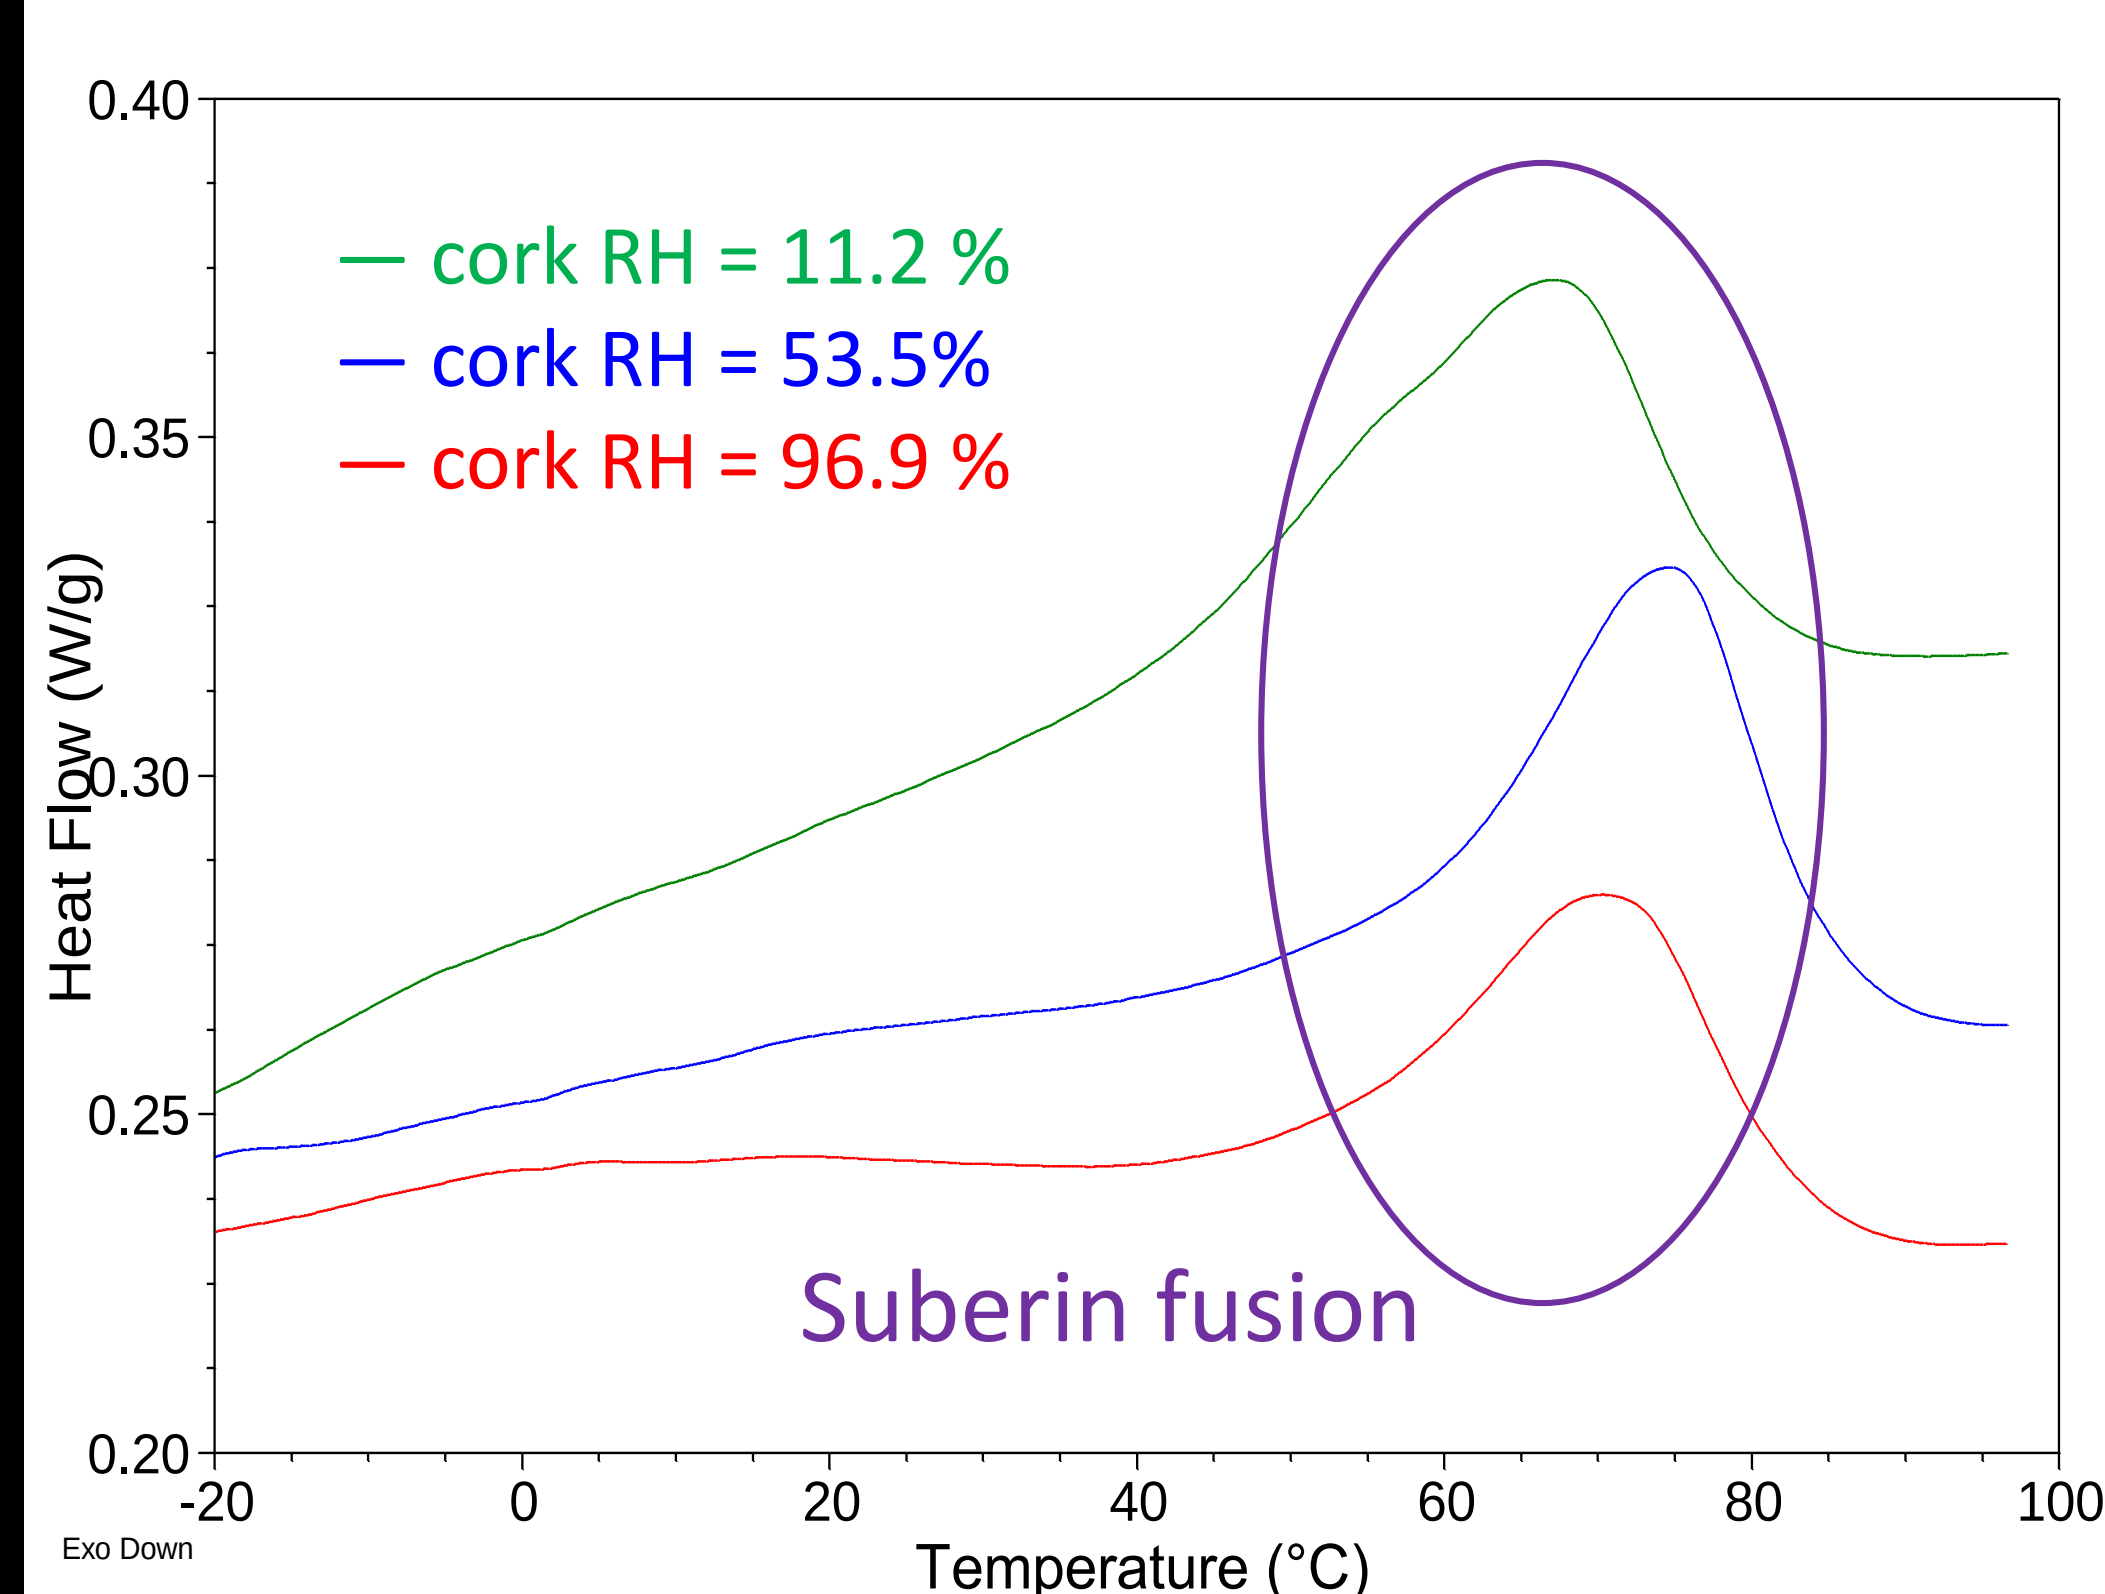

→ Difficult to identify a T_g

Conclusion

Mechanical properties of cork depend on relative humidity. Water plays an important role in cork structure with an antiplasticizing effect below 4 wt % water content, and then a plasticizing effect above this value. This can be explained by the existence of an amorphous fraction in cork which goes across its glass transition within this relative humidity range.

References

- [1] Mano, J.F. 2002. The viscoelastic properties of cork. *Journal of Membrane Science*. 37(2), 257-263.
- [2] Karbowiak, T., Gougeon, R.D., Alinc, J-B., Brachais, L., Debeaufort, F., Voilley, A., Chassagne, D., (2010). Wine oxidation and the role of cork. *Crit. Rev. Food. Sci.*, 50, 20-52
- [3] Lequin, S., Chassagne, D., Karbowiak, T., Gougeon, R. g., Brachais, L., & Bellat, J.-P. (2010). Adsorption Equilibria of Water Vapor on Cork. *Journal of Agricultural and Food Chemistry*, 58(6), 3438-3445.